



BRIGHTONLITE CEMENT

PRODUCT DESCRIPTION

Adelaide Brighton Cement produces Brightonlite Cement conforming to Australian Standard AS 3972 - 1997.

Brightonlite is a special purpose off white in colour, Type HE Cement.

SUPPLY

Brightonlite Cement is available in 20 kg and 40 kg multi-walled paper bags, in bulk bags and bulk from our Angaston Works and Customer Service Centres in regional areas. Brightonlite should be specified by name.

SPECIFICATION

Brightonlite Cement exceeds the minimum specification given in AS 3972, Type HE.

All products are manufactured under a third party certified manufacturing and supply quality assurance system to AS/NZS ISO 9002 (NCS Certification No 8507).

Brightonlite Cement is produced from Portland Cement Clinker and Gypsum and may contain up to 5% mineral additions.

APPLICATIONS

Brightonlite Cement versatile in its use and has numerous applications. For example, in-situ concrete, precast concrete, concrete masonry, paving blocks, concrete tiles, garden furniture, glass reinforced cement (GRC), mortar and wherever a light coloured finish is required.

Off white cements are often used for architectural purposes. Relatively high cement contents are normal in this application, the minimum recommended cement content is 355 kg/m³ of concrete with a maximum water/cement ratio of 0.55 for durability and to achieve colour density.

Brightonlite has a high C₃A content and it should not be used in any situation where sulfate attack is likely.

HANDLING AND STORAGE

Transportation may be in bulk road or in paper bags. Brightonlite Cement can be stored in concrete or steel silos for up to six (6) months or in paper bags for three (3) months. Protection against ingress of moisture must be observed throughout the handling and storage.

SAFETY INFORMATION

For safety information refer to the Material Safety Data Sheet for Portland & Blended Cement.

TYPICAL PROPERTIES

Physical Properties

Test	Typical Value	AS 3972 Requirement
Setting Time (hr:min) AS 2350.4-1987		
Initial	1:30	min 00:45
Final	2:30	max 10:00
Soundness (mm) AS 2350.5-1987		
	1	max 5
Compressive Strengths ISO-CEN mortar bars (MPa) AS 2350.11-1997		
1 Day	16 - 18	-
3 Days	39 - 41	20
7 Days	49 - 51	30
28 Days	65 - 67	-
Maximum Temperature Rise (°C) AS 2350.7-1997		
	40	-
Mortar Shrinkage (microstrain) AS 2350.13-1995		
7 Days	450	-
14 Days	650	-
21 Days	740	-
28 Days	800	-

Chemical Properties

Test	Units	Typical Values
Fineness	m ² /kg	415 - 455
Sulphur Trioxide	%	2.3
Loss on Ignition	%	2.9
Chloride	%	0.002
Equivalent Alkalies	%	0.4
Hexavalent Chromium	mg/kg	<2
Crystalline Silica Components	%	0.4
Portland Clinker	%	90 - 95
Gypsum	%	5
Mineral Addition	%	5

CONTACT POINTS

For further information contact the Sales & Marketing Department at:

Adelaide Brighton Cement
A.B.N. 96 007 870 199
62 Elder Road
BIRKENHEAD SA 5015

Telephone: (08) 8300 0300


Facsimile: (08) 8341 1591

Web Site: <http://www.adbri.com.au>




BRIGHTONLITE CEMENT

COMPRESSIVE STRENGTH DEVELOPMENT OF CONCRETE

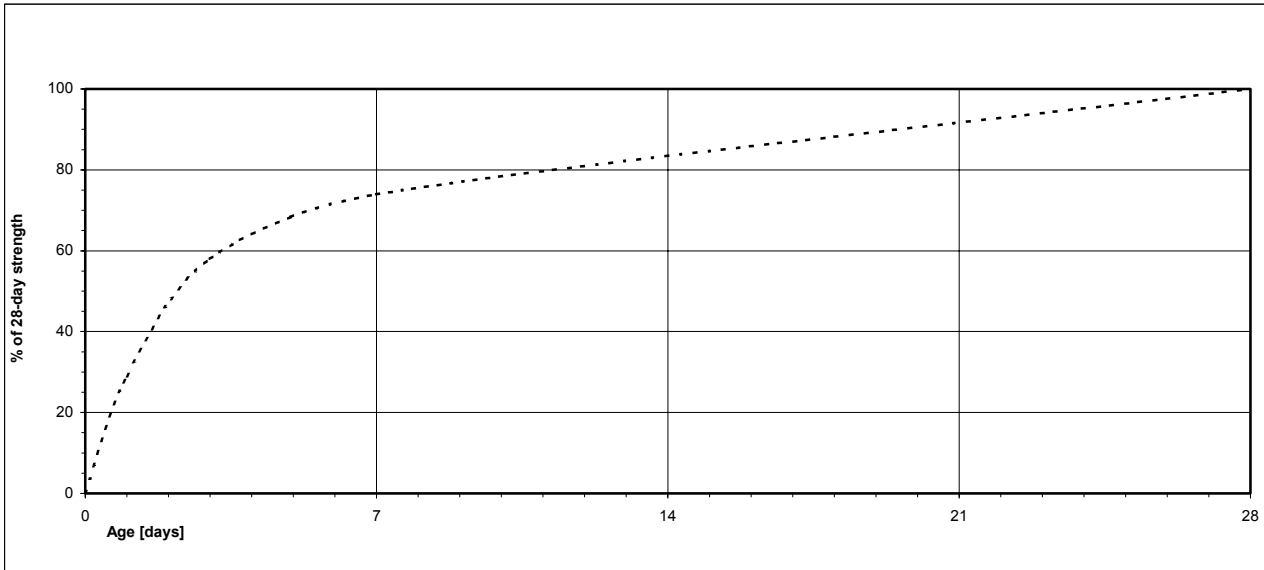

TYPE BRIGHTONLITE: WATER/CEMENT RATIO CURVES

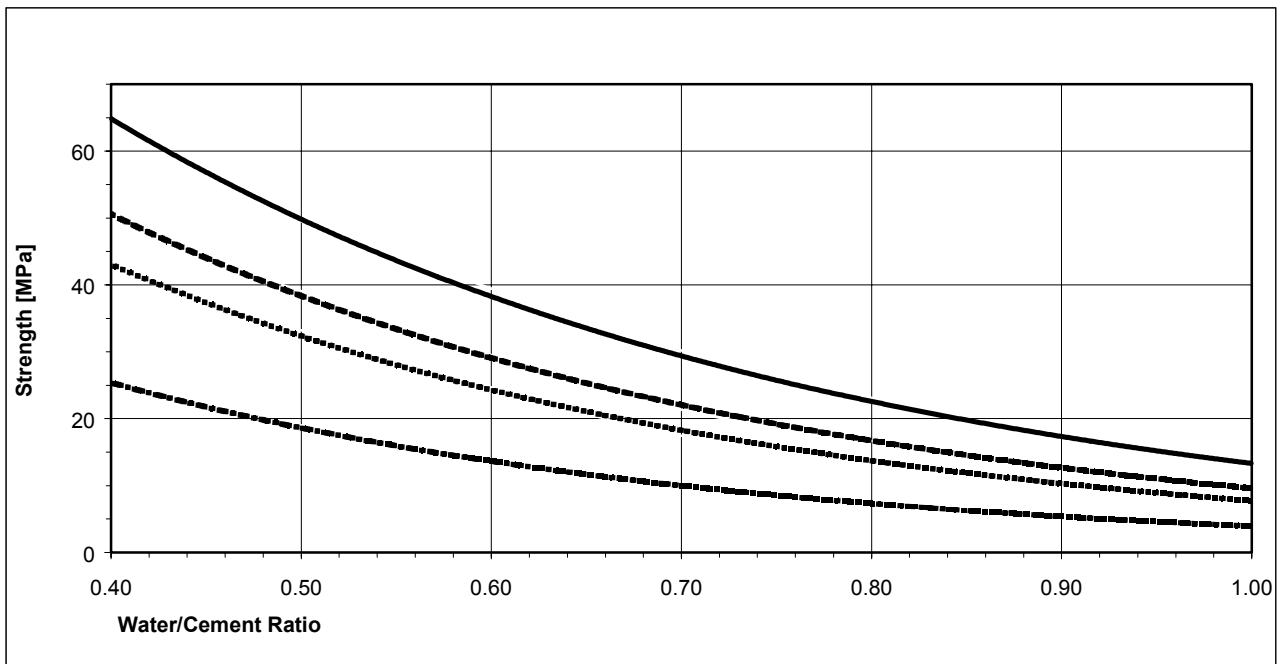

DISCLAIMER

The information contained in this sheet is for general guidance only. It does not replace the advice of professional consultants. Where unusual conditions or requirements exist seek professional advice. No liability is accepted by Adelaide Brighton Cement or the suppliers, for any associated expenses, losses, damages or costs resulting from the use of this information, as the use is beyond their control.

Incorrect use of any product, or failure to adhere to recommendations in this sheet, or those of any supplier, and any associated safety information may result in serious damage or injury.